

RILSAN® CLEAR G170

PA,MT,C12-020

Rilsan® Clear G170 is a high performance transparent polyamide resin with outstanding thermal resistance. This grade has been designed for injection molding applications.

MAIN CHARACTERISTICS

PROPERTIES	DRY / COND	UNIT	TEST STANDARD
RHEOLOGICAL PROPERTIES			
Melt Volume-Flow Rate	2 / *	cm ³ /10min	ISO 1133
Temperature	275 / *	°C	-
Load	2.16 / *	kg	-
Molding Shrinkage, parallel	0.7 / *	%	ISO 294-4, 2577
Molding Shrinkage, normal	0.7 / *	%	ISO 294-4, 2577
MECHANICAL PROPERTIES			
Tensile Modulus	2100 / 2020	MPa	ISO 527-1/-2
Yield stress	76 / 74	MPa	ISO 527-1/-2
Yield strain	8 / 9	%	ISO 527-1/-2
Nominal Strain at Break	> 50 / > 50	%	ISO 527-1/-2
Shore D Hardness, 15s	79 / *	-	ISO 7619-1
Charpy Impact Strength, +23°C	- / No Break	kJ/m ²	ISO 179/1eU
Charpy Impact Strength, -30°C	No Break / No Break	kJ/m ²	ISO 179/1eU
Charpy Notched Impact Strength, +23°C	- / 13	kJ/m ²	ISO 179/1eA
Charpy Notched Impact Strength, -30°C	- / 13	kJ/m ²	ISO 179/1eA
THERMAL PROPERTIES			
Glass Transition Temperature, 10°C/min	168 / *	°C	ISO 11357-1/-2
Temp. of Deflection Under Load, 1.80 MPa	136 / *	°C	ISO 75-1/-2
Temp. of Deflection Under Load, 0.45 MPa	150 / *	°C	ISO 75-1/-2
Vicat Softening Temperature, 50°C/h 50N	160 / *	°C	ISO 306
Coeff. of Linear Thermal Expansion, parallel	70 / *	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nominal Thickness	V-2 / *	class	IEC 60695-11-10
Thickness Tested	1.6 / *	mm	-
Yellow Card available	yes / *	-	-
Oxygen Index	26 / *	%	ISO 4589-1/-2
ELECTRICAL PROPERTIES			
Volume Resistivity	- / 1E11	Ohm*m	IEC 60093
Surface Resistivity	* / 1E12	Ohm	IEC 60093
Dielectric (Electric) Strength	- / 50	kV/mm	IEC 60243-1
Comparative Tracking Index	* / 600	-	IEC 60112

Arkema France - A French "société anonyme", registered in the Nanterre (France) Trade and Companies Register under the number 319 632 790 S0C/11-2018

Please consult Arkema's disclaimer regarding the use of Arkema's products on <https://www.arkema.com/en/products/product-safety/disclaimer/index.html>

RILSAN®
CLEAR
BY ARKEMA

RILSAN® CLEAR G170

OTHER PROPERTIES			
Water Absorption	3.8 / *	%	Sim. to ISO 62
Humidity Absorption	1.7 / *	%	Sim. to ISO 62
Density	1050 / 1050	kg/m ³	ISO 1183
OPTICAL PROPERTIES			
Luminous Transmittance	91	%	ISO 13468-1, -2

MAIN APPLICATIONS:

- Coffee machine
- Fuel filter container.- Inner layer of fiber optic and copper telephone cables resistant to rodents.- Power cables resistant to rodents.Note: This grade is not recommended by Arkema for usage in medical applications. For such applications

RILSAN® CLEAR G170 MED&NBSP;should be used.

PACKAGING:

This grade is delivered dried in sealed packaging (25 kg bags) ready to be processed.

SHELF LIFE:

Two years from the delivery. For any use above this limit, please refer to our technical services.

Arkema France - A French "société anonyme", registered in the Nanterre (France) Trade and Companies Register under the number 319 632 790 SBC/11-2018


Please consult Arkema's disclaimer regarding the use of Arkema's products on <https://www.arkema.com/en/products/product-safety/disclaimer/index.html>

RILSAN®
CLEAR
BY ARKEMA


RILSAN® CLEAR G170

DIAGRAMS


VISCOSITY-SHEAR RATE

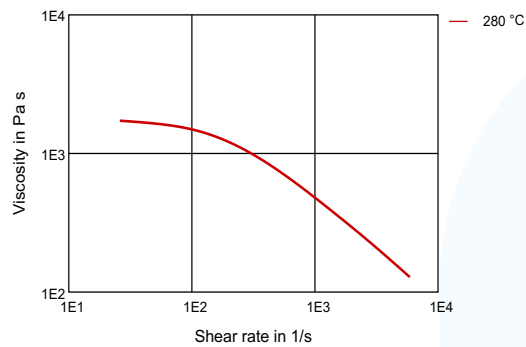


SHEARSTRESS-SHEAR RATE

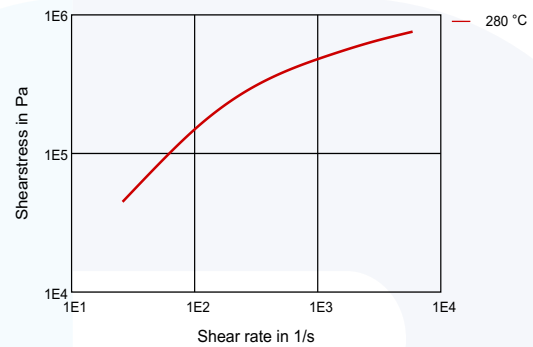

DYNAMIC SHEAR MODULUS-TEMPERATURE

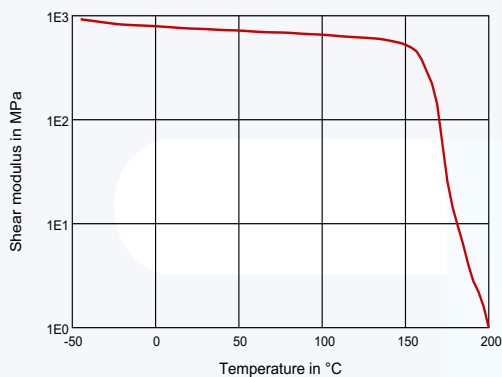

DYNAMIC TENSILE MODULUS-TEMPERATURE

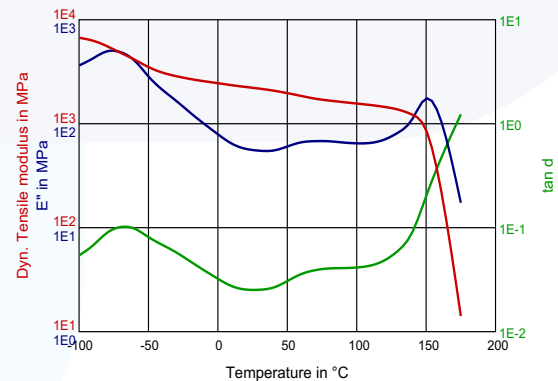


Arkema France - A French "société anonyme", registered in the Nanterre (France) Trade and Companies Register under the number 319 632 790 SBC/11-2018

Please consult Arkema's disclaimer regarding the use of Arkema's products on <https://www.arkema.com/en/products/product-safety/disclaimer/index.html>


RILSAN®
CLEAR
BY ARKEMA

RILSAN® CLEAR G170

STRESS-STRAIN

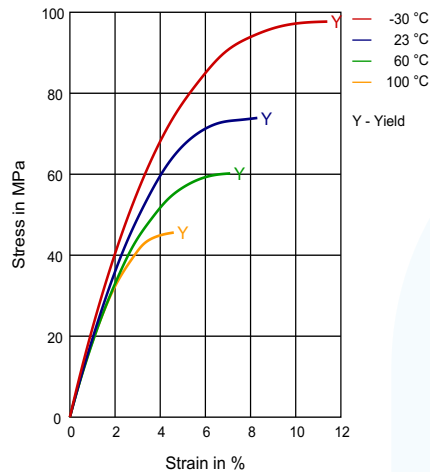

SECANT MODULUS-STRAIN

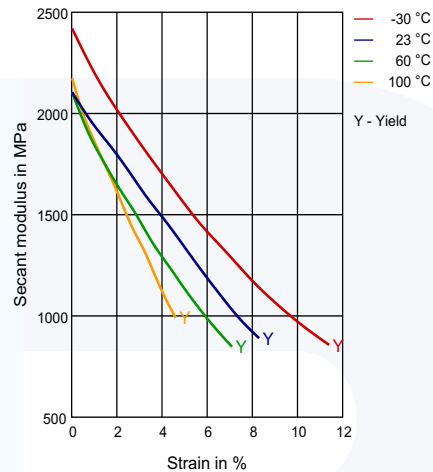

Injection molding conditions:

- Typical melt temperature (Min / Recommended / Max) : 270°C / 290°C / 310°C
- Typical mold temperature : 40 - 80 °C
- Drying time and temperature (only for bags opened for more than two hours): 4 - 6 hours at 90°C

Extrusion conditions:

- Typical melt temperature (Min / Recommended / Max) : 270°C / 280°C / 290°C
- Drying time and temperature (only for bags opened for more than two hours): 4 - 6 hours at 90°C

PROCESSING

Injection Molding, Other Extrusion

DELIVERY FORM

Pellets

SPECIAL CHARACTERISTICS

Transparent

REGIONAL AVAILABILITY

North America, Europe, Asia Pacific, South and Central America, Near East/Africa

Arkema France - A French "société anonyme" registered in the Nanterre (France) Trade and Companies Register under the number 319 632 790 S00711-2018

Please consult Arkema's disclaimer regarding the use of Arkema's products on <https://www.arkema.com/en/products/product-safety/disclaimer/index.html>

Rilsan® Clear is a registered trademark of Arkema
© 2022 Arkema Inc. All rights reserved.

rilsamid.com

Arkema Inc. – Technical Polymers

900 First Avenue
King of Prussia, PA 19406
Tel.: +1 610 205 7000
Fax: +1 610 205 7497
arkema-america.com

RILSAN®
CLEAR
BY **ARKEMA**

Headquarters: Arkema France

420, rue d'Estienne d'Orves
92705 Colombes Cedex – France
Tel.: +33 1 49 00 80 80
Fax: +33 1 49 00 83 96
arkema.com